

IN-LB

Inch-Pound Units

SI

International System of Units

# Durable Concrete—Guide

Reported by ACI Committee 201

ACI PRC-201.2-23



American Concrete Institute  
*Always advancing*



## **Durable Concrete—Guide**

Copyright by the American Concrete Institute, Farmington Hills, MI. All rights reserved. This material may not be reproduced or copied, in whole or part, in any printed, mechanical, electronic, film, or other distribution and storage media, without the written consent of ACI.

The technical committees responsible for ACI committee reports and standards strive to avoid ambiguities, omissions, and errors in these documents. In spite of these efforts, the users of ACI documents occasionally find information or requirements that may be subject to more than one interpretation or may be incomplete or incorrect. Users who have suggestions for the improvement of ACI documents are requested to contact ACI via the errata website at <http://concrete.org/Publications/DocumentErrata.aspx>. Proper use of this document includes periodically checking for errata for the most up-to-date revisions.

ACI committee documents are intended for the use of individuals who are competent to evaluate the significance and limitations of its content and recommendations and who will accept responsibility for the application of the material it contains. Individuals who use this publication in any way assume all risk and accept total responsibility for the application and use of this information.

All information in this publication is provided “as is” without warranty of any kind, either express or implied, including but not limited to, the implied warranties of merchantability, fitness for a particular purpose or non-infringement.

ACI and its members disclaim liability for damages of any kind, including any special, indirect, incidental, or consequential damages, including without limitation, lost revenues or lost profits, which may result from the use of this publication.

It is the responsibility of the user of this document to establish health and safety practices appropriate to the specific circumstances involved with its use. ACI does not make any representations with regard to health and safety issues and the use of this document. The user must determine the applicability of all regulatory limitations before applying the document and must comply with all applicable laws and regulations, including but not limited to, United States Occupational Safety and Health Administration (OSHA) health and safety standards.

Participation by governmental representatives in the work of the American Concrete Institute and in the development of Institute standards does not constitute governmental endorsement of ACI or the standards that it develops.

Order information: ACI documents are available in print, by download, through electronic subscription, or reprint and may be obtained by contacting ACI.

Most ACI standards and committee reports are gathered together in the annually revised the ACI Collection of Concrete Codes, Specifications, and Practices.

**American Concrete Institute**  
**38800 Country Club Drive**  
**Farmington Hills, MI 48331**  
**Phone: +1.248.848.3700**  
**Fax: +1.248.848.3701**

[www.concrete.org](http://www.concrete.org)

# Durable Concrete—Guide

Reported by ACI Committee 201

Thomas J. Van Dam, Chair

R. Douglas Hooton, Secretary  
(and Chair of last incremental update)

Lawrence L. Sutter,  
Secretary of last incremental update

Matthew P. Adams\*  
Reza Ahrabli  
James M. Aldred  
Oscar R. Antommattei  
Jon B. Ardahl†  
Mohamed Bassuoni  
Anthony F. Bentivegna\*  
Bruce Blair  
Andrew J. Boyd  
Paul W. Brown  
Ramon L. Carrasquillo

Tara Cavalline\*  
Rachel J. Detwiler  
Jonathan E. Dongell  
Thano Drimalas  
Kevin J. Folliard  
Harvey H. Haynes  
Jason H. Ideker  
Donald J. Janssen  
Roy H. Keck  
Mohammad S. Khan  
Kimberly E. Kurtis

Michael L. Leming  
Tyler Ley  
Darmawan Ludirdja  
Mohamad Nagi  
Robert E. Neal  
Charles K. Nmai  
Karthik H. Obla  
Robert C. O'Neill  
Kyle Austin Riding  
David A. Rothstein  
Hannah C. Schell

April Snyder\*  
David G. Tepke  
Michael D. A. Thomas  
Paul J. Tikalsky  
David Trejo  
Thomas J. Van Dam\*  
Orville R. Werner II  
Terry J. Willems  
Michelle L. Wilson

## Consulting Members

W. Barry Butler  
Bernard Erlin  
Odd E. Gjorv†  
Charles J. Hookham

Francis Innis\*  
Alexander M. Leshchinsky  
Stella Lucie Marusin  
Howard H. Newlon Jr.

Mauro J. Scali®  
W. Calvin McCall\*  
George V. Teodoru  
Niels Thaulow

J. Derle Thorpe  
Claude B. Trusty Jr.  
Terry J. Willems\*

\*Voting or consulting member of incremental revision.

†Deceased.

*This guide describes specific types of concrete deterioration. Each chapter contains a discussion of the mechanisms involved and the recommended requirements for individual components of concrete, quality considerations for concrete mixtures, construction procedures, and influences of the exposure environment, which are all important considerations to ensure concrete durability.*

*This guide was developed for conventional concrete but is generally applicable to specialty concretes; however, specialty concretes, such as roller-compacted or pervious concrete, may have unique durability-related issues that deserve further attention that are not addressed herein.*

**Keywords:** abrasion resistance; alkali-aggregate reaction; chemical attack; curing; deterioration; durability; freezing and thawing; physical salt attack; sulfate attack.

ACI Committee Reports and Guides are intended for guidance in planning, designing, executing, and inspecting construction. This document is intended for the use of individuals who are competent to evaluate the significance and limitations of its content and recommendations and who will accept responsibility for the application of the material it contains. The American Concrete Institute disclaims any and all responsibility for the stated principles. The Institute shall not be liable for any loss or damage arising therefrom.

Reference to this document shall not be made in contract documents. If items found in this document are desired by the Architect/Engineer to be a part of the contract documents, they shall be restated in mandatory language for incorporation by the Architect/Engineer.

## CONTENTS

### CHAPTER 1—INTRODUCTION AND SCOPE, p. 2

- 1.1—Introduction, p. 2
- 1.2—Scope, p. 3

### CHAPTER 2—DEFINITIONS, p. 3

- 2.1—Definitions, p. 3

### CHAPTER 3—MASS TRANSPORT, p. 3

- 3.1—Introduction, p. 3
- 3.2—Transport processes in nonreactive porous media, p. 4
- 3.3—Factors affecting mass transport in concrete, p. 5
- 3.4—Measurement of transport properties, p. 8
- 3.5—Obtaining durable concrete, p. 10

### CHAPTER 4—FREEZING AND THAWING OF CONCRETE, p. 10

- 4.1—Introduction, p. 10

ACI PRC-201.2-23 supersedes ACI 201.2R-16 and was published in May 2023.

Copyright © 2023, American Concrete Institute.

All rights reserved including rights of reproduction and use in any form or by any means, including the making of copies by any photo process, or by electronic or mechanical device, printed, written, or oral, or recording for sound or visual reproduction or for use in any knowledge or retrieval system or device, unless permission in writing is obtained from the copyright proprietors.

4.2—Frost attack of concrete made with durable aggregates, p. 11

4.3—Frost attack of concrete made with nondurable aggregates, p. 17

#### **CHAPTER 5—AGGREGATE REACTIONS, p. 19**

5.1—Alkali-aggregate reaction, p. 19

5.2—Iron sulfide mineral oxidation in concrete, p. 32

#### **CHAPTER 6—SULFATE ATTACK, p. 35**

6.1—External sulfate attack, p. 35

6.2—Internal sulfate attack, p. 41

6.3—Seawater and brine exposure, p. 43

#### **CHAPTER 7—CHEMICAL ATTACK, p. 44**

7.1—General, p. 44

7.2—Seawater, p. 45

7.3—Acid attack, p. 46

7.4—Fresh water, p. 47

7.5—Carbonation, p. 48

7.6—Industrial chemicals, p. 48

7.7—Deicing and anti-icing chemicals, p. 49

7.8—Environmental structures, p. 50

#### **CHAPTER 8—PHYSICAL SALT ATTACK, p. 51**

8.1—Introduction, p. 51

8.2—Occurrence, p. 52

8.3—Background, p. 52

8.4—Mechanism, p. 53

8.5—Testing, p. 53

8.6—Key factors, p. 55

8.7—Protection, p. 55

8.8—Recommendations, p. 56

#### **CHAPTER 9—CORROSION OF METALS AND DEGRADATION OF OTHER MATERIALS EMBEDDED IN CONCRETE, p. 56**

9.1—Introduction, p. 56

9.2—General principles of corrosion initiation in concrete, p. 56

9.3—Propagation of corrosion, p. 57

9.4—Corrosion-related properties of concreting materials, p. 58

9.5—Mitigating corrosion, p. 59

9.6—Corrosion of prestressed steel reinforcement, p. 61

9.7—Degradation of materials other than steel, p. 62

9.8—Summary, p. 63

#### **CHAPTER 10—ABRASION, p. 63**

10.1—Introduction, p. 63

10.2—Testing concrete for resistance to abrasion, p. 63

10.3—Factors affecting abrasion resistance of concrete, p. 65

10.4—Recommendations for obtaining abrasion-resistant concrete surfaces, p. 66

10.5—Abrasives and studded tire and tire chain wear on concrete, p. 67

10.6—Skid resistance of pavements, p. 67

10.7—Erosion, p. 68

#### **CHAPTER 11—SUMMARY, p. 68**

#### **CHAPTER 12—REFERENCES, p. 69**

Authored documents, p. 71

### **CHAPTER 1—INTRODUCTION AND SCOPE**

#### **1.1—Introduction**

Concrete is the most widely used construction material in the world. The design, detailing, and execution of concrete to resist weathering action, chemical attack, abrasion, and other processes of deterioration over its intended service life will determine its durability. Durable concrete will retain its original form, quality, and serviceability when exposed to its environment. Properly designed, proportioned, transported, placed, finished, and cured concrete can provide decades of service with little or no maintenance, yet certain conditions or environments exist that can lead to concrete deterioration. Deterioration mechanisms are either chemical or physical in nature and may originate from within the concrete, or may be the result of the external environmental exposure. Chemical and physical attacking mechanisms often work synergistically. Depending on the nature of the attack, distress may be concentrated in the paste, aggregate, or reinforcing components of the concrete, or a combination thereof.

The various factors influencing durability and a particular mechanism of deterioration should be considered in the context of the environmental exposure of the concrete. In addition, consideration should be given to the microclimate to which the specific structural element is to be exposed. The type and severity of deterioration of a given structure may be affected by its proximity to sources of deleterious agents or agents that facilitate distress, exposure to wind, precipitation, or temperature. For instance, exterior girders in a bridge structure may be exposed to a more aggressive environment than interior girders.

The concept of service life is increasingly used for the design of new structures. To produce concrete suitable for a particular application, required service life, design requirements, and expected exposure environments, both macro and micro, should be determined before defining the necessary materials and mixture proportions.

The use of good materials and proper mixture proportioning will not, by itself, ensure durable concrete. Appropriate placement practices and workmanship are essential to the production of durable concrete. Fresh concrete can be consolidated and molded to the shape desired to serve its intended purpose. During this stage, numerous properties significantly influencing the durability of the hardened concrete are established. Pore structure development, air-void system formation, material uniformity, and potential for cracking are established at early ages and are important to the ultimate durability of concrete. As such, durable concrete requires the application of good quality control during construction. Inspection and testing by trained and certified

personnel can help ensure the use of durable mixtures and proper practices.

## 1.2—Scope

This guide discusses the important mechanisms of concrete deterioration and gives recommendations on how to mitigate or minimize such damage. This guide also addresses durability by first discussing the importance of mass transport and then addressing specific modes of attack in separate chapters. These include freezing and thawing, alkali-aggregate reaction (AAR), sulfate attack, aggressive chemical attack, physical salt attack, corrosion of metals and other embedded materials, abrasion, or a combination of these. Fire resistance of concrete and cracking are not addressed directly. Fire resistance is covered in [ACI 216.1](#) and cracking is covered in [ACI 224R](#) and [ACI 224.1R](#). While cracking does impact the durability of concrete in severe exposures, the different causes of cracking and their specific impacts are not discussed. Cracking is only mentioned in general terms regarding its impact on fluid ingress.

## CHAPTER 2—DEFINITIONS

### 2.1—Definitions

Please refer to the latest version of ACI Concrete Terminology for a comprehensive list of definitions. Definitions provided herein complement that resource.

**advective transport**—transfer of heat or matter via the bulk motion of a fluid.

**alkali loading (or content)**—total amount of equivalent alkalis ( $\text{Na}_2\text{O}_e$ ) in a concrete mixture expressed as mass per volume.

**calcium sulfoaluminate cement**—product obtained by pulverizing clinker containing mainly ye'elite  $[\text{Ca}_4(\text{AlO}_2)_6\text{SO}_4]$  that is often used in expansive cements and ultra-high-early-strength cements.

**diffusion**—movement of species, such as ions, gas, or vapor, from an area of higher concentration to an area of lower concentration, independent of the bulk motion of a fluid.

**electrical migration**—transport of electrons or ions due to an electric potential gradient.

**ice lens**—layer of ice, generally parallel to the exposed surface of the concrete, that can produce internal damage and also lead to scaling or delamination.

**leaching**—dissolution and removal of soluble components such as calcium hydroxide from concrete.

**permeability**—the ability of a given concrete to permit liquids or gases to pass through.

**permeation**—flow of a liquid, gas, or vapor within a solid under the action of a pressure gradient.

**physical salt attack**—mechanism in which concrete or mortar is damaged as a result of salt crystallization pressure.

**reactive silica**—form of silica, often amorphous or crypto-crystalline, that dissolves when in contact with concrete pore solution having a sufficiently high concentration of hydroxyl ions.

**salt weathering**—form of deterioration most commonly observed in arid climates where exposure to soluble salts and cyclic variations in temperature and relative humidity can lead to salt crystallization.

**thaumasite**—silicate mineral, colorless to white prismatic hexagonal crystals typically as acicular radiating groups, with the chemical formula  $\{[\text{Ca}_3\text{Si}(\text{OH})_6 \cdot 12(\text{H}_2\text{O})](\text{SO}_4)(\text{CO}_3)\}$ .

## CHAPTER 3—MASS TRANSPORT

### 3.1—Introduction

Concrete is a multiphase porous medium consisting of a multiscale porous cement paste matrix with aggregate inclusions. Liquid and gas may be present in any pores and micro-cracks. As such, it is susceptible to the ingress and movement of substances (fluids or ions) from its environment within and through its pore system. This chapter discusses the transport of gases, liquids, and ions in solution through concrete ([Lichtner et al. 1996](#); [Baer 1988](#); [Hearn et al. 2006](#); [Hall and Hoff 2012](#)). Methods for improving the durability of concrete and some of the common test methods used to measure the transport properties, along with their advantages and limitations with regard to assessing concrete durability, are also discussed. It is recognized that the rate of ingress of fluids and ions will increase by the presence of cracks. However, the specific influences of different types of cracks and crack widths are not discussed herein.

The ingress of gases, liquids, or ions in solution through concrete may initiate chemical processes, physical processes, or both, that affect the durability of the concrete under a given set of service conditions. Water itself may be harmful because of its ability to leach calcium hydroxide (CH) from the hardened cement paste and because of osmotic pressures generated as water flows to sites of higher alkalinity ([Powers et al. 1954](#); [Powers 1975](#); [Helmuth 1960b,c](#)). In addition, water may also be acidic or carry harmful dissolved chemicals, such as chlorides or sulfates, into the concrete. The ingress of gases such as oxygen and carbon dioxide through the concrete pores can contribute to the corrosion of steel reinforcement.

Different substances may interact with components of the concrete in different ways; therefore, transport of a substance through concrete is unique to that substance. For example, water can hydrate previously unhydrated cement particles or leach calcium. Chloride ions may be bound by the hydration products of cement or supplementary cementitious materials (SCMs). The size of the molecules or ions that are transported through the concrete, viscosity of the fluid, valence of the ions, and other ionic species present also affect the transport properties. Thus, permeability and diffusivity must be expressed in terms of the substance that is migrating through the concrete. In general, concrete with transport properties that limit the rate of ingress of external agents is not immune to chemical deterioration, but the effects are mainly near the exposed surfaces, so the concrete tends to be more durable.

### 3.2—Transport processes in nonreactive porous media

This section provides a brief overview of the transport processes of fluids (gases and liquids) and ions in solution within a nonreactive porous medium. This is a simplifying assumption because concrete changes chemically and physically with time in response to its environment. Physical changes, chemical changes, or both, in the internal structure of the porous medium resulting from interactions with the migrating fluids or ions are not discussed herein. The transport pathways described here include:

- (a) Transport by permeation
- (b) Advective transport
- (c) Hydrodynamic dispersion
- (d) Diffusion within the pores
- (e) Transport due to electrostatic interactions or electrical migration

**Martín-Pérez et al. (2001)** modeled transport related to corrosion of reinforcement in concrete based on chloride transport, moisture diffusion, heat transfer, and oxygen transport using a two-dimensional (2-D) finite element model. They used a modified version of Fick's second law.

**Johannesson (2003)** developed a theoretical model for diffusion of different types of ions in concrete pore solution. The model incorporates diffusion caused by concentration gradients of ions (for example, due to drying), internal electrical potential, convection, effects of changes in moisture content, and mass exchange of ions between solution and solid hydration phases.

**Chung and Consolazio (2005)** developed a finite difference model to simulate heat and mass transport in rapid heating conditions, such as fires in reinforced concrete structures. The model accounts for the interference between liquid and gas phases, slip-flow effects in steam flow, and the interference of steel reinforcement in moisture movement in concrete.

**3.2.1 Transport by permeation**—Permeation is the flow of a fluid under the action of a pressure gradient. Permeability is the property that characterizes the ease with which fluid passes through a porous material under a pressure gradient. For a steady laminar flow through a saturated porous medium, the fluid flow is related to the hydraulic pressure gradient according to Darcy's law.

$$dq/dt = K_1 A \Delta h / l \quad (3.2.1)$$

where  $dq/dt$  is the flow (expressed as a rate);  $K_1$  is the permeability coefficient;  $A$  is the cross-sectional area;  $\Delta h$  is the hydraulic head; and  $l$  is the thickness of the specimen. The permeability coefficient  $K_1$  is the rate of discharge of water under laminar flow conditions through a unit cross-sectional area of a porous medium under a unit hydraulic gradient and standard temperature conditions. Darcy's law indicates that for a given cross-sectional area and permeability coefficient, the flow is proportional to the hydraulic gradient  $\Delta h/l$ . Under service conditions, flow is three-dimensional, and the concrete may not be saturated. In concrete, the permeability coefficient may change with increased hydration, cracking,

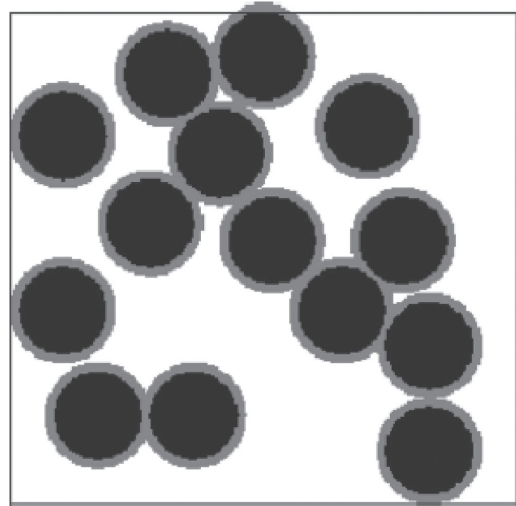


Fig. 3.2.1—Graphical representation of a simple percolation theory model used to model the permeability of concrete.

or changes in the pore structure due to various physical and chemical processes.

Permeability coefficients of plastic portland cement pastes of 0.5 water-cement ratio ( $w/c$ ), calculated from measurements of bleeding, ranged from  $5$  to  $8 \times 10^{-7}$  m/s for four cements with different chemical composition but the same specific surface ( $180 \text{ m}^2/\text{kg}$  by the Wagner turbidimeter). The permeability coefficient of mature paste (for example, at greater than 28 days of age) is between 1 millionth and one 10 millionth of that of fresh paste. It ranges from  $1 \times 10^{-15}$  to  $1.2 \times 10^{-12}$  m/s for  $w/c$  ranging from 0.3 to 0.7 (**Powers et al. 1954**).

To understand the effects of microstructure on the permeability of concrete, **Bentz et al. (1999)** at the National Institute of Standards and Technology (NIST) used percolation theory. One useful application of percolation theory is the examination of the time needed for a material to progress through a complex maze (**Stauffer and Aharony 1992**). This maze consists of areas that can allow free movement, as well as areas that impede the transport of a fluid to different degrees. These models can be made in two and three dimensions and can include the effects of cracks. **Lu et al. (2012)** were able to use a three-dimensional version of the NIST model to predict chloride ingress into cracked concrete.

Work has also been done by NIST that models changes in the properties of these systems with time. This allows the change in the microstructure of the concrete to be examined with time and observe the effects on the ability of a fluid to move through the system.

A graphical representation of a simple percolation theory model has been used by **Bentz (2000)** to model the transport of a fluid through concrete in two dimensions, as shown in Fig. 3.2.1. Very dense areas are used for aggregates. Moderately dense material is used for the cement paste and low-density material is used to model the interfacial transition zone (3.3.4).

**3.2.2 Advective transport**—Advective transport refers to the movement of molecules and ions with the bulk solution